


SPECIFICATION CONTROL DRAWING

55PC6121

TITLE WIRE, RADIATION-CROSSLINKED, MODIFIED, ETFE-INSULATED, TIN-COATED COPPER, GENERAL PURPOSE, LIGHT AIRFRAME, 600 VOLT	Date 03-16-00	Revision C
---	------------------	---------------

This specification sheet forms a part of the latest issue of Raychem Specification 55PC.

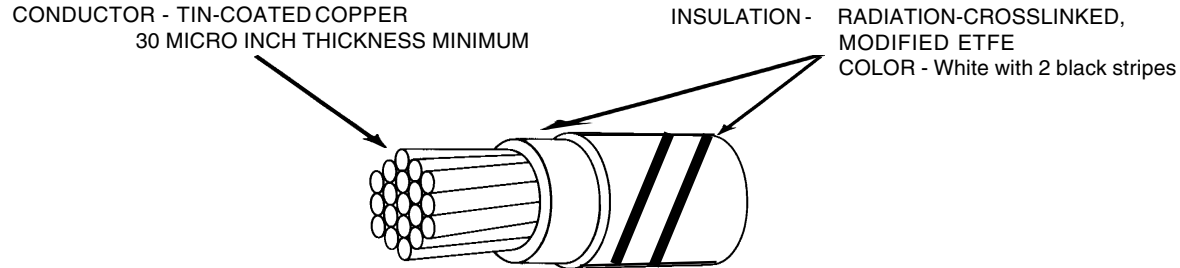

CONSTRUCTION DETAILS

PART NUMBER	WIRE SIZE (AWG)	CONDUCTOR STRANDING (number x AWG)	CONDUCTOR DIAMETER (in.)			FINISHED WIRE						
			LOWER SPEC LIMIT	TARGET VALUE	UPPER SPEC LIMIT	MAXIMUM RESISTANCE AT 20°C (ohms/1000 ft.)	DIAMETER (in.)			WEIGHT (lbs/1000 ft.)		
							LOWER SPEC LIMIT	TARGET VALUE	UPPER SPEC LIMIT	LOWER SPEC LIMIT	TARGET VALUE	UPPER SPEC LIMIT
55PC6121-22-900	22	19 x 34	.0285	.0293	.0301	16.2	.0438	.0455	.0472	2.74	2.90	3.06
55PC6121-20-900	20	19 x 32	.0365	.0375	.0385	9.88	.0523	.0540	.0557	4.19	4.38	4.57
55PC6121-18-900	18	19 x 30	.0452	.0464	.0476	6.23	.0616	.0635	.0654	6.28	6.59	6.90

WIRE RATINGS AND ADDITIONAL REQUIREMENTS

TEMPERATURE RATING: 150°C
 Maximum continuous conductor temperature
VOLTAGE RATING: 600 volts (rms)
CROSSLINK VERIFICATION: 300 ± 3°C for 1 hour
IDENTIFICATION AND COLOR STRIPING DURABILITY:
 125 cycles (250 strokes) (minimum), 500 g weight
INSULATION ELONGATION AND TENSILE STRENGTH:
 Total Insulation,
 Elongation, 50% (minimum)
 Tensile Strength, 5000 lbf/in² (minimum)
INSULATION FLAWS:
 Impulse Dielectric Test, 8.0 kV (peak)
INSULATION THICKNESS: .008 in. (nominal) total insulation

SHRINKAGE: 230 ± 3°C for 1 hour, 0.125 in. (maximum) in 12 in.
SPOOLING:
 Minimum lengths, 500 ft.
 Place orange flag on each splice
STRIPE WIDTH: .022 in. (maximum)
STRIPE INTERVALS: Per MIL-STD-681 (2 inch maximum)
VOLTAGE WITHSTAND TEST (POST ENVIRONMENTAL):
 2500 volts (rms)

MARKING: Mark wire in green ink at 1.5 inch (nominal) distance between marks. Example: " 18 AWG "
 Mark shall be read horizontally for AWG size 20 and 18
 Mark shall be read vertically for AWG size 22

NOTES: - THIS WIRE MEETS ALL REQUIREMENTS OF BMS13-48T10C1, EXCEPT IDENTIFICATION AS MODIFIED HEREIN.
 - STRIPING INK MEETS RAYCHEM SPECIFICATION RT1404 WHICH INCLUDES IMMERSSED I.R. AND DWV TESTING.

COLORS, STRIPES AND COLOR CODE DESIGNATORS SHALL BE IN ACCORDANCE WITH MIL-STD-681.

Raychem

300 Constitution Drive, Menlo Park, California 94025
 1-800-2 Raychem Fax: 1-650-361-6297