CUSTOMER DRAWING

Slit Adhesive Sleeve (S-1017)

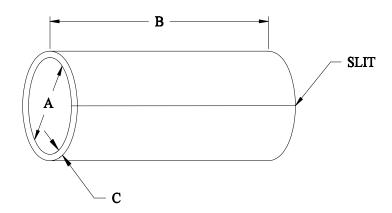


Table 1: <u>Dimensions</u> (inches)

PART DESCRIPTION	EXTRUDED ID (A)	CUT LENGTH (B)	EXTRUDED WALL (C)
SAS-090-038-1017	.090 ± .005	0.38 ± .050	0.024 ± .005
SAS-090-075-1017	.090 ± .005	0.75 ± .050	0.024 ± .005
SAS-090-1-1017	$.090 \pm .005$	1.00 ± .050	0.024 ± .005
SAS-115-075-1017	.115 ± .005	0.75 ± .050	0.032 ± .005
SAS-115-1-1017	.115 ± .005	1.00 ± .050	0.032 ± .005
SAS-160-075-1017	.160 ± .005	0.75 ± .050	0.032 ± .005
SAS-160-1-1017	.160 ± .005	1.00 ± .050	0.032 ± .005
SAS-200-075-1017	.200 ± .005	0.75 ± .050	0.035 ± .005
SAS-200-1-1017	.200 ± .005	1.00 ± .050	0.035 ± .005

Color: Amber

₹ Tyco Electi	ronics	Tyco Electronics Corp. 300 Constitution Drive, Menlo Park, CA. 94025	Raychem Molded Parts	TITLE:	SPLIT ADH	ESIVE SL	EEVE
Unless otherwise specified, dimensions are in inches. [Metric dimensions are shown in brackets] TOLERANCES: ANGLES: Tyco Electronics reserves the right to amend this		DOCUMENT NO.: SAS-XXX-XXX-1017					
0.00 N/A 0.0 N/A 0 N/A	N/A ROUGHNES S IN MICRON	drawing at any time. Users s	ing at any time. Users should evaluate the bility of the product for their application.		ION: D	DATE: August 14, 2008	
PREPARED BY: UNGU		ECO NUMBER: ECO-08-020204	CAGE CODE : 06090		SCALE: -NA-	SIZE:	SHEET: 1 of 3

© 2004 –2008 Tyco Electronics Corporation. All rights reserved.

CUSTOMER DRAWING

Table 2: Properties

Property	Unit	Requirements	Test Method
Physical	Offic	Requirements	Test wethou
Visual		No foreign matter, voids, pinholes.	
Specific Gravity		0.95 ± 0.05	ASTM D 792
Softening Point	°C	120 ± 10	ASTM E 28
Low Temperature Impact Brittleness	°C	-20 maximum	ASTM D 746
Adhesive Peel Polyolefin Polychloroprene Polyvinylchloride Chemical*	lbs/in width	20 minimum 10 minimum 15 minimum	Note 1
Water Absorption	Percent	1.0 maximum	ASTM D 570
Fungus Resistance		Rating of 1 or less	ASTM G 21
Fluid Resistance* Weight Change after 7 days/23 ± 3°C (75 ± 5°F) 3 X 1-inch specimens	Percent		ASTM D 543
Detergent Solution (#12) Hydraulic Fluid (MIL-PRF-87257 or MIL-PRF-83282) Lube Oil (MIL-PRF-7808L) ASTM Oil (#49)		3 maximum 10 maximum 5 maximum 15 maximum	
Electrical*			
Volume Resistivity	ohm-cm	10 ¹⁰ minimum	ASTM D 257
Dielectric Strength	V/mil	500 minimum	ASTM D 149

^{*}Test specimens shall be prepared in the form of 6 x 6 x .075-inch compression molded slabs. Molding temperature shall be 150 \pm 3°C (302 \pm 5°F).

Acceptance Tests: Visual, Dimensions, Specific Gravity

DOCUMENT NO.:	ECO NUMBER:	REV.:	DATE:	SHEET:
SAS-XXX-XXX-1017	ECO-08-020204	D	August 14, 2008	2 of 3

CUSTOMER DRAWING

Note 1: Adhesive Peel Strength

Polyolefin

Shrink a 6-inch length of size 1-1/2 inch tubing RNF-100 Type 2* on a glass-laminated plastic or metal tube, 1 inch in diameter, and approximately 1 foot long, with a Thermofit Model 500B Thermogun* or equivalent. Cool to room temperature, lightly abrade with No. 320 emery cloth, and wipe with MEK. Spiral wrap S-1017* tape on the recovered tubing, with a 50% overlap. Place a strip of 3/4-inch-wide masking tape lengthwise on the adhesive tape to hold it in place and to provide unbonded ends to insert into the tensile tester.

Abrade and clean the inside surface of three 1-1/2 inch lengths of size 1-1/2 inch RNF-100 Type 2. Place them on the prepared mandrel so that they are about 1/2 inch apart, and shrink with the Thermogun. Place the assembly in an oven for 10 minutes at $150 \pm 3^{\circ}$ C ($302 \pm 5^{\circ}$ F).

Cool to room temperature, and cut along one edge of the masking tape to remove the bonded assembly from the mandrel. Cut a 1-inch wide specimen from the center of each double thickness. Insert the unbonded ends in a tensile tester operating at 2 inches per minute. Make readings of peel strength at every 1/2 inch of jaw separation after 1 inch initial separation. The average of 5 readings shall define peel strength.

<u>Polychloroprene</u>

Repeat above procedure, except use NTFR* tubing.

Polyvinylchloride

Repeat above procedure, except use Thermofit PVC* tubing.

- *Obtainable from Tyco Electronics/Raychem Corporation.
- +S-1017 tape is made from the same lot of material as SAS-1017.

Tyco Electronics Corporation/Raychem reserves the right to amend this specification at any time. Users should evaluate the suitability of the product for their application.

DOCUMENT NO.:	ECO NUMBER:	REV.:	DATE:	SHEET:
SAS-XXX-XXX-1017	ECO-08-020204	D	August 14, 2008	3 of 3

X-ON Electronics

Largest Supplier of Electrical and Electronic Components

Click to view similar products for Spiral Wraps, Sleeves, Tubing & Conduit category:

Click to view products by TE Connectivity manufacturer:

Other Similar products are found below:

6984850001 8426-11 5026790001 5026800002 5026810001 5026820001 502679N003 RAY-101-3.0(100) 100-001A250 1200068 RBK-ESS-CROSS-10.0-X-8MM AA59569R34T0781 100-003A078 561-W48BK/C CQ50393001 CQ50453001 102-051-016 167-00217 CS-A900T THP6B 106815-0381 5418A-500-CU 7644-T-110 8424-8 8425-8 4545 AF1554-NA005 G1101/4-BK005 G1201/8-BK002 P1050-BK005 P10517-CL005 P10522-BK005 PF13012-BK002 PF1307/8-BK005 PF20016-NA005 PF2003-NA005 PF2007/16-NA005 PF2008-NA005 PIF-200-1/2A-NA008 SW21-NA002 SW14-WH005 TFT20011-NA002 TFT2009-NA002 TFT25024-NA001 XS200N1/4-BK002 1200135 1200194 1205137 CCF-1 1/2-8-12 SC-3/4